

# NATIONAL BUREAU OF STANDARDS REPORT

10 165

~~Not for Publication  
For Reference~~

Progress Report

October 1 through December 31, 1969

DEVELOPMENT OF METHODS OF TEST  
FOR QUALITY CONTROL OF PORCELAIN ENAMELS



U.S. DEPARTMENT OF COMMERCE  
NATIONAL BUREAU OF STANDARDS

## NATIONAL BUREAU OF STANDARDS

The National Bureau of Standards<sup>1</sup> was established by an act of Congress March 3, 1901. Today, in addition to serving as the Nation's central measurement laboratory, the Bureau is a principal focal point in the Federal Government for assuring maximum application of the physical and engineering sciences to the advancement of technology in industry and commerce. To this end the Bureau conducts research and provides central national services in four broad program areas. These are: (1) basic measurements and standards, (2) materials measurements and standards, (3) technological measurements and standards, and (4) transfer of technology.

The Bureau comprises the Institute for Basic Standards, the Institute for Materials Research, the Institute for Applied Technology, the Center for Radiation Research, the Center for Computer Sciences and Technology, and the Office for Information Programs.

**THE INSTITUTE FOR BASIC STANDARDS** provides the central basis within the United States of a complete and consistent system of physical measurement; coordinates that system with measurement systems of other nations; and furnishes essential services leading to accurate and uniform physical measurements throughout the Nation's scientific community, industry, and commerce. The Institute consists of an Office of Measurement Services and the following technical divisions:

Applied Mathematics—Electricity—Metrology—Mechanics—Heat—Atomic and Molecular Physics—Radio Physics<sup>2</sup>—Radio Engineering<sup>2</sup>—Time and Frequency<sup>2</sup>—Astrophysics<sup>2</sup>—Cryogenics.<sup>2</sup>

**THE INSTITUTE FOR MATERIALS RESEARCH** conducts materials research leading to improved methods of measurement standards, and data on the properties of well-characterized materials needed by industry, commerce, educational institutions, and Government; develops, produces, and distributes standard reference materials; relates the physical and chemical properties of materials to their behavior and their interaction with their environments; and provides advisory and research services to other Government agencies. The Institute consists of an Office of Standard Reference Materials and the following divisions:

Analytical Chemistry—Polymers—Metallurgy—Inorganic Materials—Physical Chemistry.

**THE INSTITUTE FOR APPLIED TECHNOLOGY** provides technical services to promote the use of available technology and to facilitate technological innovation in industry and Government; cooperates with public and private organizations in the development of technological standards, and test methodologies; and provides advisory and research services for Federal, state, and local government agencies. The Institute consists of the following technical divisions and offices:

Engineering Standards—Weights and Measures—Invention and Innovation—Vehicle Systems Research—Product Evaluation—Building Research—Instrument Shops—Measurement Engineering—Electronic Technology—Technical Analysis.

**THE CENTER FOR RADIATION RESEARCH** engages in research, measurement, and application of radiation to the solution of Bureau mission problems and the problems of other agencies and institutions. The Center consists of the following divisions:

Reactor Radiation—Linac Radiation—Nuclear Radiation—Applied Radiation.

**THE CENTER FOR COMPUTER SCIENCES AND TECHNOLOGY** conducts research and provides technical services designed to aid Government agencies in the selection, acquisition, and effective use of automatic data processing equipment; and serves as the principal focus for the development of Federal standards for automatic data processing equipment, techniques, and computer languages. The Center consists of the following offices and divisions:

Information Processing Standards—Computer Information—Computer Services—Systems Development—Information Processing Technology.

**THE OFFICE FOR INFORMATION PROGRAMS** promotes optimum dissemination and accessibility of scientific information generated within NBS and other agencies of the Federal government; promotes the development of the National Standard Reference Data System and a system of information analysis centers dealing with the broader aspects of the National Measurement System, and provides appropriate services to ensure that the NBS staff has optimum accessibility to the scientific information of the world. The Office consists of the following organizational units:

Office of Standard Reference Data—Clearinghouse for Federal Scientific and Technical Information<sup>3</sup>—Office of Technical Information and Publications—Library—Office of Public Information—Office of International Relations.

<sup>1</sup> Headquarters and Laboratories at Gaithersburg, Maryland, unless otherwise noted; mailing address Washington, D.C. 20234.

<sup>2</sup> Located at Boulder, Colorado 80302.

<sup>3</sup> Located at 5285 Port Royal Road, Springfield, Virginia 22151.

# NATIONAL BUREAU OF STANDARDS REPORT

## NBS PROJECT

421.04-12--4212270

February 9, 1970

## NBS REPORT

10 165

*Not for publication or  
for reference.*

Progress Report

October 1 through December 31, 1969

## DEVELOPMENT OF METHODS OF TEST FOR QUALITY CONTROL OF PORCELAIN ENAMELS

by

M. D. Burdick and M. A. Baker

Porcelain Enamel Institute Research Associateship  
National Bureau of Standards

### IMPORTANT NOTICE

NATIONAL BUREAU OF STANDARDS  
for use within the Government.  
and review. For this reason, the  
whole or in part, is not authorized  
Bureau of Standards, Washington  
the Report has been specifically

Approved for public release by the  
director of the National Institute of  
Standards and Technology (NIST)  
on October 9, 2015

and accounting documents intended  
subjected to additional evaluation  
listing of this Report, either in  
Office of the Director, National  
the Government agency for which  
copies for its own use.



U.S. DEPARTMENT OF COMMERCE  
NATIONAL BUREAU OF STANDARDS



# I. The Adherence of Porcelain Enamels Direct-to-Steel

## INTRODUCTION

The objective of this study is to develop a new method or to modify existing methods for measuring the quality of adherence in direct-on porcelain enamel production.

A number of plant visits have been made to survey existing adherence methods and to assess industry needs in this area of quality control.

The work described in this report was intended to compare, quantify and correlate several existing destructive, deformation techniques related to the evaluation of adherence.

## RESULTS AND DISCUSSION

### A. Enamel Systems

A series of ten cover coats direct-to-steel was described in the previous report in this series. Each enamel system was designated by two code letters; the first identified the five different enamel compositions: A, B, C, D and X; and the second letter identified the pickling treatment: N, M, P and O described in Table 1. The enamel systems in the above described series were used in the present evaluations.

### B. Deformation Methods Employed

1. A "stretch" test described by J. E. Sams<sup>1/</sup> produced a flat, uniformly deformed specimen area which was thought to contribute to a more objective visual or instrumental rating than did the concave surface obtained from an indentation-type of deformation. Strip specimens, about 3/4 inch in width and 4 to 6 inches long were de-enameled at each end by sand blasting to provide uniform gripping in a tensile machine. Load was applied beyond the yield point of the steel to provide an elongation of between 8 and 10 per cent. When adherence was poor, after the bulk of the enamel layer chipped away, mainly bare metal of a light grey color was exposed in the stretched area. With improved adherence, greater amounts of glass were left attached to the substrate which resulted in darker grey colors and decreased reflectance. Those enamel systems showing the best adherence (estimated by other methods) appeared dark grey after stretching and the reflectance of the pulled specimen area was thought to be influenced more by the adherence than by the color of the original glass coating.

#### 2. Impact Deformation Test

A conventional drop-weight test was used to estimate adherence of the direct-on systems for comparison with other estimates. A five pound weight falling through a distance of 16 inches impacted a one-half inch diameter ball indenter resting on the specimen and centered over a 5/8 inch bottomless die. The indentations were evaluated with a PEI adherence meter to obtain numerical results. The adherence index was calculated as:  $AI = \frac{75 - X}{75} \times 100$  where X

was the average number of counts obtained for each indentation. This modified method of calculation was intended to compensate for a smaller area of indentation than that obtained with a one inch ball indenter in the PEI press. This method of calculation was previously used by Afflerbach. <sup>2/</sup>



### 3. Adherence Tests with the PEI Equipment

All of the direct-on systems were evaluated with deformations obtained with the 20 gage and Research dies, with and without water immersion after deformation, and after immersion in still and ultrasonically agitated water. The amount of bare metal was estimated in the usual way with the PEI counter.

#### C. Relative Severity of the Deformation Methods

A compilation of all adherence estimates is given in Table 2. The use of the 20 gage die, with a depth of 0.156 inch, produced mild deformations. The enamel layers were cracked in six of the ten systems tested but remained attached to the substrate in such a way that no bare metal was found by the needle probes. The remaining four systems, obviously with poorer adherence, had lowered adherence indices. It is not unreasonable, in view of later results, to assume that there may be differences in adherence among the six systems which were not resolved with the 20 gage die deformations. It was desired to use a modified die form or other treatments which would increase the severity of the test procedure and resolve differences in adherence which might be expected to obtain within a series of systems deliberately designed to include a wide range of adherence values. The difficulty of this operation is obvious. How can one resolve differences in adherence which are only assumed, without a referee test for adherence measurement?

Water immersion of deformed specimens before counting appeared to be an effective way to obtain increased removal of cracked enamel (increased severity of the test procedure). This is illustrated in Figures 1 and 2.

The use of the deeper research die (depth 0.190 in.) appeared to be effective in increasing the severity of the test procedure as shown in Figure 3. The adherence indices obtained with the drop weight test appeared to be still lower and are also shown in Figure 3. It may be noted, however, that the drop weight indices fail to resolve any assumed differences between systems XP, CP, and BO. Perhaps this drop weight procedure is too severe for the range of adherence values among these specimens. Even the ball peen hammer (a classical method for demonstrating lack of bond) showed a difference in adherence between BO on the one hand and the "poorly" pickled enamels X and C.

Comparison among the deformation methods shown in Figures 1, 2, and 3 suggest that the order of increasing severity was as follows:

1) (least severe) 20 gage die, dry; 2) 20 gage die, wet; 3) research die, wet, and 4) drop weight test. The mildest deformation method failed to resolve assumed differences among the good adherence enamel systems, and the drop weight deformations failed to separate several of the poor adherence systems. As shown in Figure 3 it is suggested that the research die results in intermediate deformations which, after immersion in water, give the best resolution on both ends of the quality scale of adherence for these cover coats direct-to-steel. This conclusion is based on the assumption of real differences in adherence among these systems.

Figure 4 shows a comparison between deformed specimen immersion in still water and in a water bath which was ultrasonically agitated. The small differences in adherence indices obtained following these treatments were not considered statistically significant. The difference in results as a function of immersion time (one and ten minutes) might be real for systems of intermediate adherence indices (such as AM).

#### D. Correlation Comparison of Several Methods

Four methods of adherence estimation can be compared in Table 3 by observing the relative order or rank in which these tests placed these enamel systems. There are minor differences in rank for the various enamels. AN, for example, ranks best by three test procedures and second best by the fourth, while CP is rated poorest by three procedures and second poorest by the fourth. The consensus of these procedures is reflected in a mean rank in the last column. The mean rank allows a comparison with the intuitive judgment based on the degree of the pickling treatment these specimens received. Enamel A was ranked superior (1.25) when applied to normally pickled steel and intermediate (4.0) when applied to an intermediate pickled steel. In the same way, XN had a better adherence than XP; and CM was rated better than CP. Enamel D, however, in all tests, exhibited better adherence when applied to a medium pickled steel than when applied to a steel which had received a normal metal preparation. This unexpected result may be associated with the marked difference in enamel thickness for DM and DN or it may result from an inadvertent mix-up of these two enamel groups.

The lower part of Table 3 gives values for correlation coefficients for the several method-pairs. In general, coefficients between 0.81 and 0.95 indicated good agreement between these destructive, deformation methods or modifications.



## PLANS FOR NEXT REPORT PERIOD

A. A new bank of direct-on cover coated specimens has been ordered. The new specimens will be coated with the same (white) enamel composition applied to a single lot of decarburized steel and pickled at the same time. Six different grades of adherence will be sought through control of the nickel deposition. One hundred specimens of each grade will be prepared and several hundred steel blanks will be retained in dry storage for future use.

B. An adhesion tester (button test) designed to cover the range of 0 to 2000 psi has been purchased and its motorization has been completed with the exception of receiving the motor, delivery of which is expected momentarily. A program of testing will be undertaken with the new specimens:

1. To determine the reproducibility to be expected when using the readily available deformation tests, and...

2. To determine the reproducibility of the direct pulling button test and to seek some validity for the deformations tests through comparison with direct pulling values.

C. Explore the possibility of a modified tape peel test similar to that used for adherence of organic coatings.

## MISCELLANEOUS ACTIVITIES

The second meeting of a Direct-On-Adherence Advisory Committee (DOAAC) was held at NBS on January 14, 1970. This committee consists of representatives from (1) the steel producers, (2) the frit producers, (3) the appliance industry and (4) NBS. Volunteers from among the steel and frit producers are preparing the specimen bank mentioned above. Several subcommittees have been appointed to support the Direct-On Adherence Study.

W. E. Pierce (PEI) and M. D. Burdick visited three appliance manufacturers early in January to observe presently used adherence measurement techniques, to survey the needs in the industry in the adherence testing area and to obtain suggested parameters which might be considered in designing a plant control test. Other visits may be arranged.

## REFERENCES

1. Stretch Testing - A New Method of Measuring the Attachment of Porcelain Enamel to Sheet Metal, J. E. Sams, PEI Forum 5 p. 73, (1940).
2. Correlation Between Direct-On Cover Coat Adherence and Chippage, H. W. Afflerbach, PEI Forum 25 p. 69, (1963).

TABLE 1

Cover Coats Direct-to-Steel  
on 20 gage decarburized enameling steel

Pickling treatment requested:

|        |     |                       |                           |   |   |   |
|--------|-----|-----------------------|---------------------------|---|---|---|
| Normal | (N) | 2-3 g/ft <sup>2</sup> | metal removed plus Nickel |   |   |   |
| Medium | (M) | 1.0                   | "                         | " | " | " |
| Poor   | (P) | 0.5                   | "                         | " | " | " |
| Zero   | (O) | (not pickled)         |                           |   |   |   |

| Designation | Color   | Coating<br>Thickness<br>mils | Pickling treatment<br>reported:    |                               |
|-------------|---------|------------------------------|------------------------------------|-------------------------------|
|             |         |                              | Metal Removed<br>g/ft <sup>2</sup> | Ni added<br>g/ft <sup>2</sup> |
| AN          | White   | 3.6                          | 2.7                                | 0.14                          |
| AM          | "       | 4.2                          | 1.2                                | .13                           |
| BN          | Avocado | 3.5                          | *                                  | *                             |
| BO          | "       | 4.2                          | none                               | none                          |
| CM          | White   | 4.9                          | *                                  | *                             |
| CP          | "       | 5.0                          | *                                  | *                             |
| DN          | Copper  | 4.4                          | 2.25                               | 0.11                          |
| DM          | tone    | 6.6                          | 1.0                                | 0.10                          |
| XN          | "       | 4.5                          | 1.92                               | 0.09                          |
| XP          | "       | 4.9                          | 0.45                               | 0.05                          |

\*Not reported.

Specimens were supplied through the courtesy  
of the following firms:

Chicago Vitreous Corp.  
Ferro Corporation  
Glidden-Durkee Division of SCM  
Ingram-Richardson, Inc.  
O. Hommel Company

TABLE 2

Comparison of Several Procedures for Estimating the Adherence Index <sup>a/</sup>

| <u>Enamel System</u>                            | AN   | BN  | DM  | XN   | CM               | AM   | XP   | DN   | CP   | BO | <sup>b/</sup><br>n |
|---|------|-----|-----|------|------------------|------|------|------|------|----|--------------------|
| <u>Test Methods</u>                             |      |     |     |      |                  |      |      |      |      |    |                    |
| 20 gage die, Dry <sup>c/</sup>                  | 100  | 100 | 100 | 100  | 98               | 100  | 81   | 71   | 45   | 6  | 5                  |
| 20 " " Wet <sup>c/</sup>                        | 100  | 100 | 97  | 87   | 86               | 77   | 48   | 39   | 20   | 9  | 5                  |
| Research die, Dry                               | 99   | 99  | 90  | 87   | 83 <sup>e/</sup> | 84   | 28   | 26   | 30   | 1  | 3                  |
| Research die, Wet                               | 97   | 99  | 85  | 69   | 36 <sup>f/</sup> | 53   | 24   | 25   | 18   | 0  | 3                  |
| Research die, 30 sec.<br>in water <sup>h/</sup> | 99   | 100 | 85  | 64   | 45 <sup>g/</sup> | 41   | 24   | 27   | 23   | 0  | 3                  |
| Research die, 10 min.<br>in water <sup>h/</sup> | --   | 98  | --  | --   | --               | 32   | --   | --   | 17   | -- | 3                  |
| Drop Weight <sup>i/</sup>                       | 86   | 62  | 75  | 31   | 40               | 41   | 0    | 19   | 0    | 0  | 12                 |
| Mean Value,<br>All Methods                      | 98   | 97  | 91  | 79   | 73               | 65   | 43   | 42   | 29   | 4  | --                 |
| Stretch Test,<br>Reflectance                    | 10.5 | --  | 8.6 | 12.8 | 16.7             | 14.1 | 16.1 | 16.2 | 21.1 | -- |                    |

<sup>a/</sup> Using PEI Adherence meter.<sup>b/</sup> n = number of indentations upon which Adherence Index was based.<sup>c/</sup> The indices indicated as "Dry" were measured on specimens at least 30 minutes after deformation. The indices by the "Wet" method were obtained after 15 minutes water immersion, followed by oven drying.<sup>e/</sup> Based on measurements of 23 specimens.<sup>f/</sup> Based on measurements of 13 specimens.<sup>g/</sup> Based on measurements of 10 specimens after one minute immersion in ultrasonic water.<sup>h/</sup> The immersion was in ultrasonically agitated water.<sup>i/</sup> The drop weight involved a deformation by a one-half inch round tup, energized by a five pound weight dropped through a distance of 16 inches.

# Comparison of Results Obtained for Estimating Adherence by Four Deformation Methods

| 20 ga. die<br>Wet | Research die<br>Wet | Drop<br>Weight | Stretch<br>Test | Enamel<br>System | Mean<br>Rank |
|-------------------|---------------------|----------------|-----------------|------------------|--------------|
| AI Rank           | AI Rank             | AI Rank        | Ref'l Rank      |                  |              |
| AN 100 1          | AN 97 1             | AN 86 1        | DM 8.6 1        | AN               | 1.25         |
| DM 97 2           | DM 85 2             | DM 75 2        | AN 10.5 2       | DM               | 1.75         |
| XN 87 3           | XN 69 3             | AM 41 3        | XN 12.8 3       | XN               | 3.5          |
| CM 86 4           | AM 53 4             | CM 40 4        | AM 14.1 4       | AM               | 4.0          |
| AM 77 5           | CM 36 5             | XN 31 5        | XP 16.1 5       | CM               | 5.0          |
| XP 48 6           | DN 25 6             | DN 19 6        | DN 16.2 6       | DN               | 6.25         |
| DN 39 7           | XP 24 7             | CP 0 7.5       | CM 16.7 7       | XP               | 6.4          |
| CP 20 8           | CP 18 8             | XP 0 7.5       | CP 21.1 8       | CP               | 7.8          |

# The Correlation Coefficients Between the Four Methods for Estimating Adherence

|               | 20 gage, wet | Research, wet | Drop Weight | Stretch |
|---------------|--------------|---------------|-------------|---------|
| 20 gage, wet  | --           | 0.95          | 0.83        | 0.83    |
| Research, wet |              | --            | 0.90        | 0.88    |
| Drop Weight   |              |               | --          | 0.81    |
| Stretch       |              |               |             | --      |





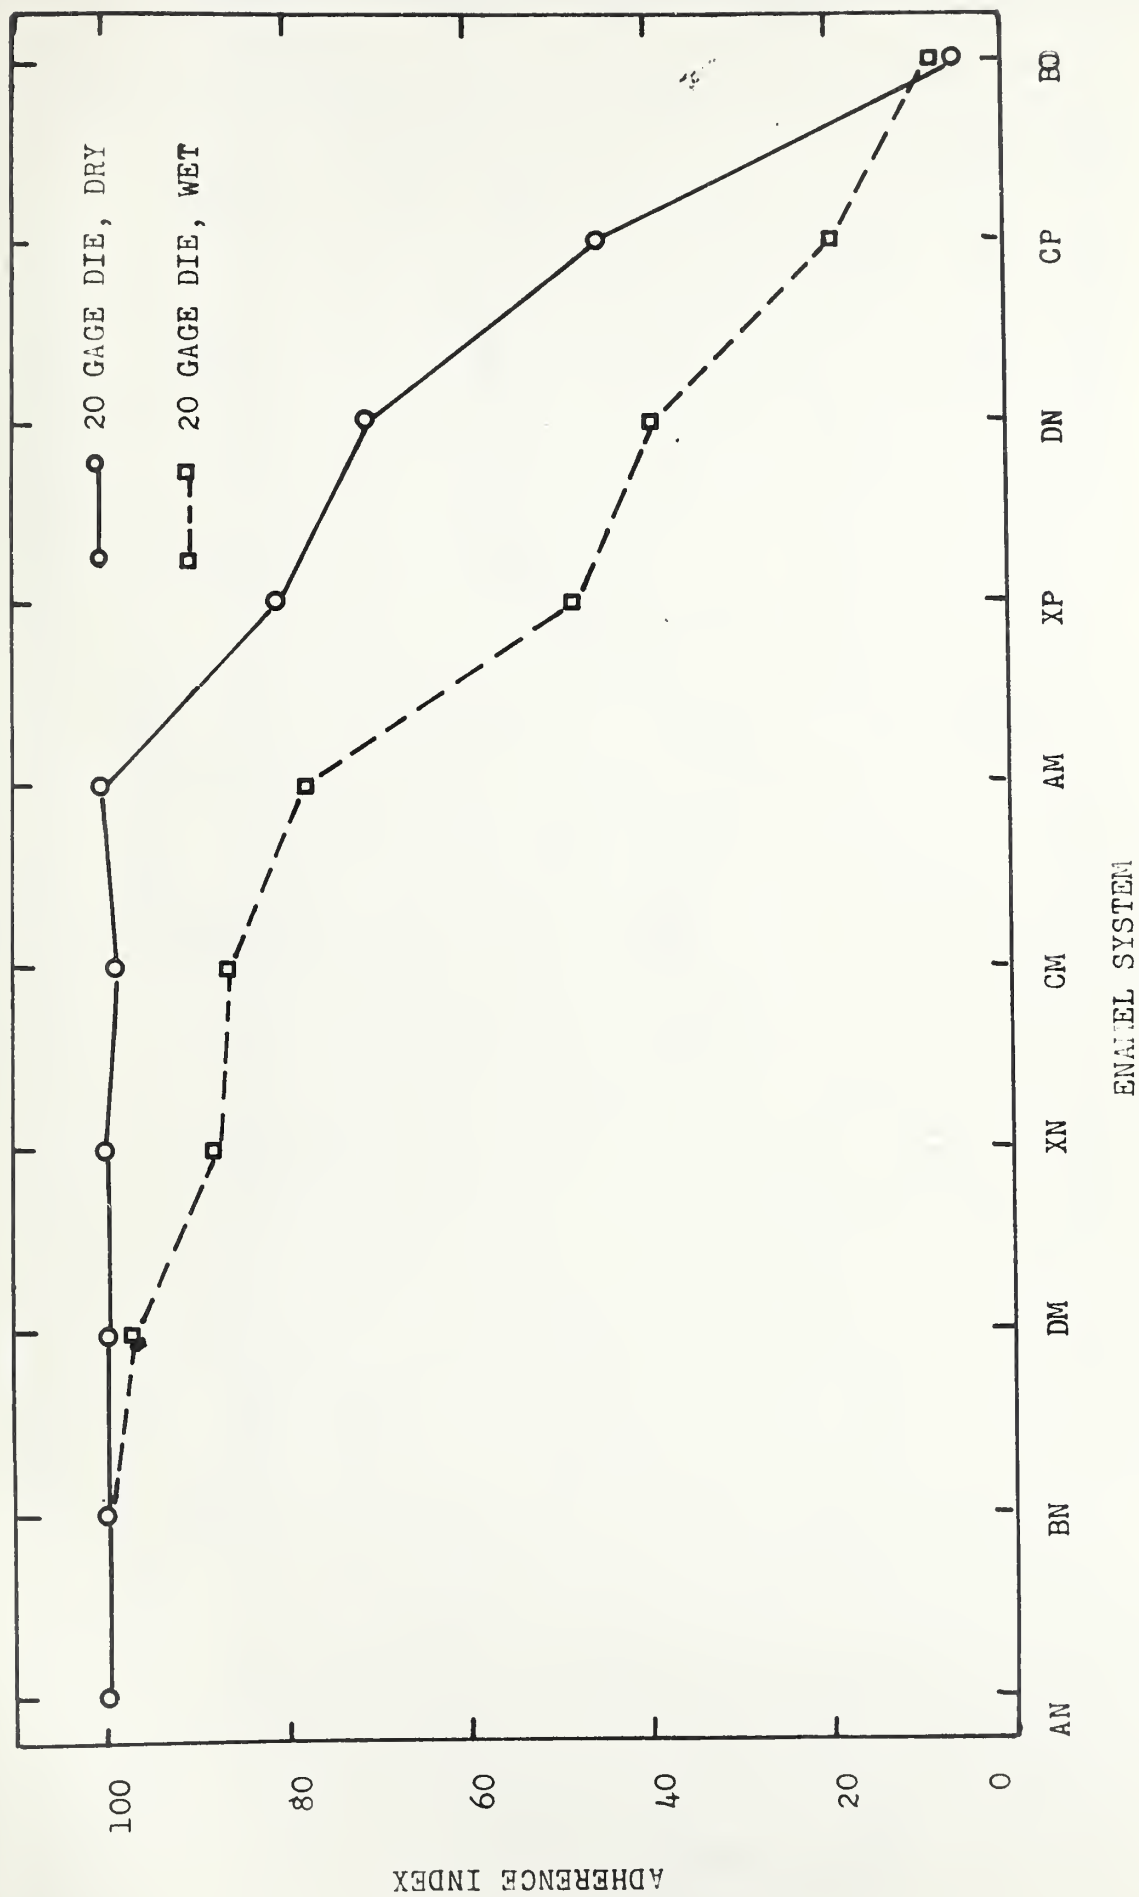


Figure 1. Comparison of Adherence Indices after various Deformation Treatments.

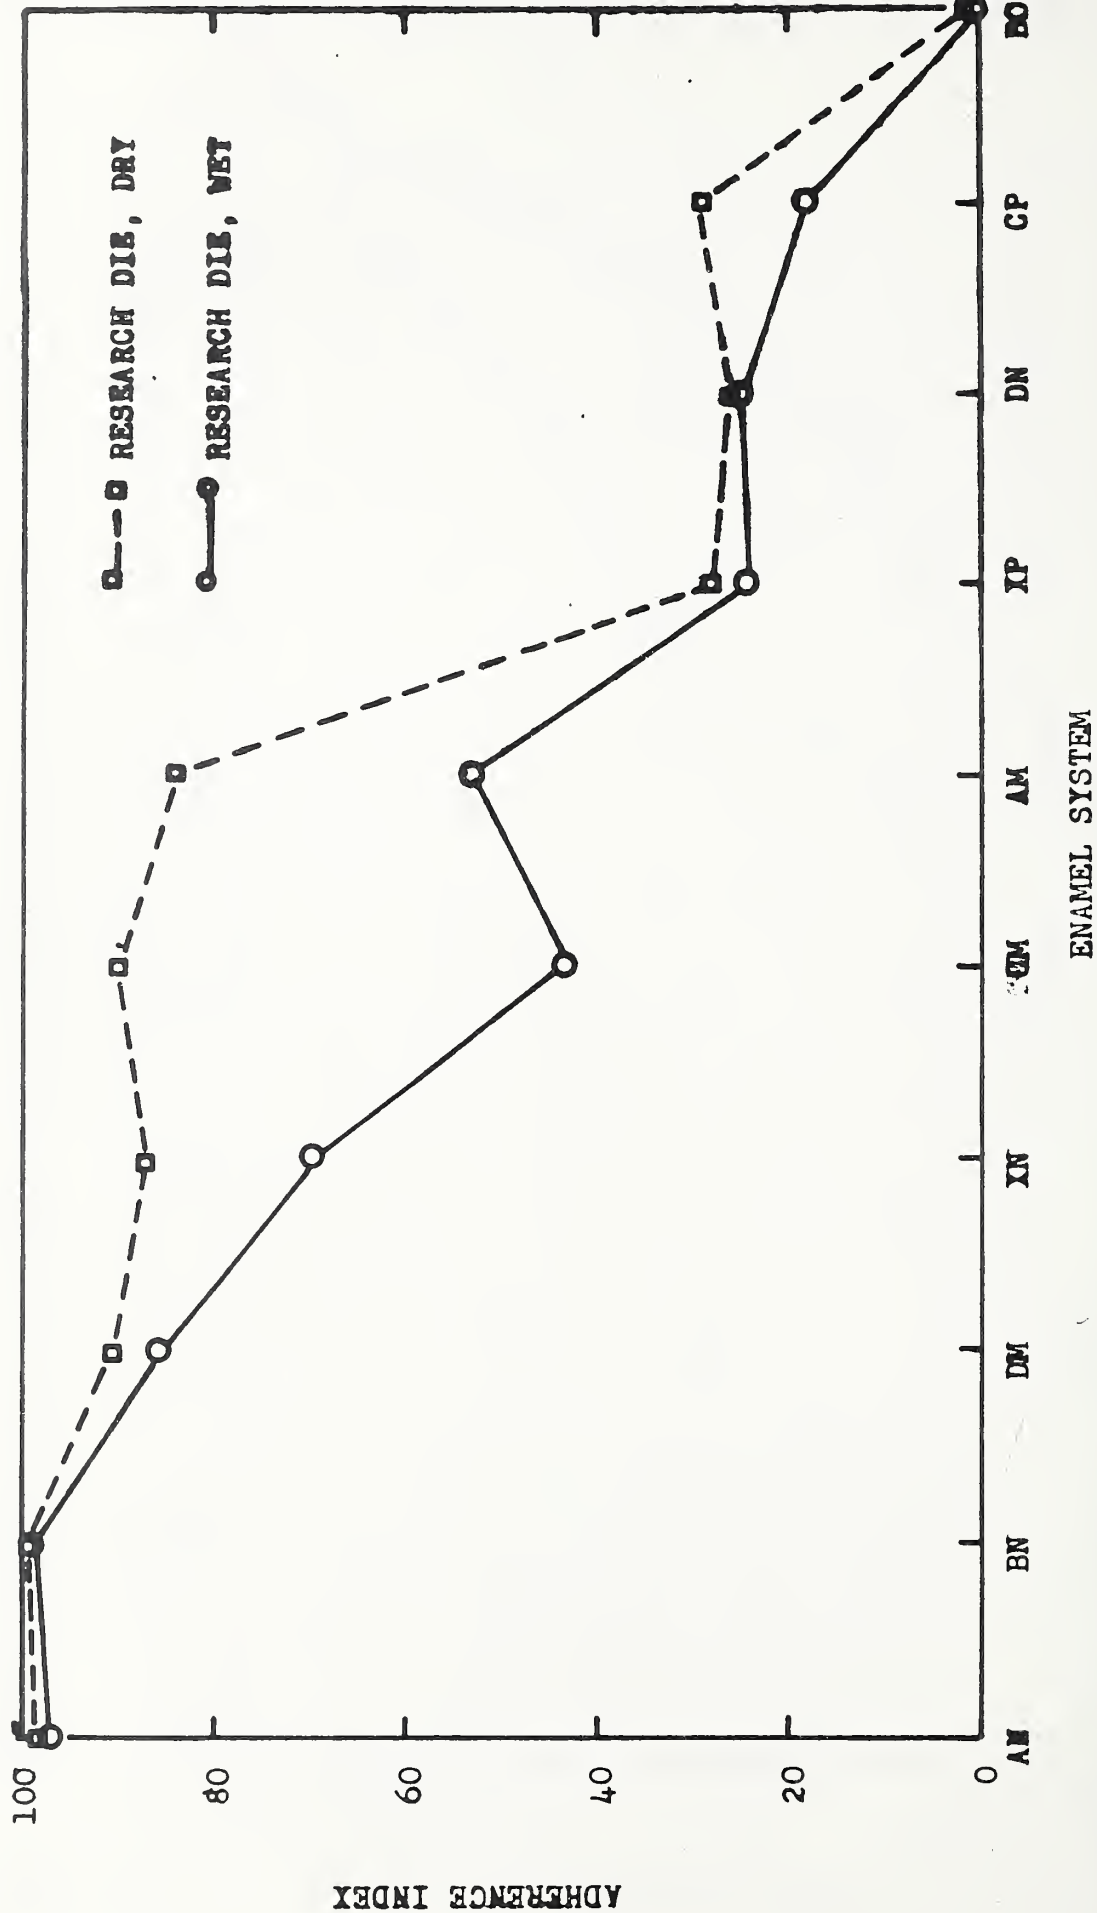


Figure 2. Comparison of Adherence Indices after various Deformation Treatments


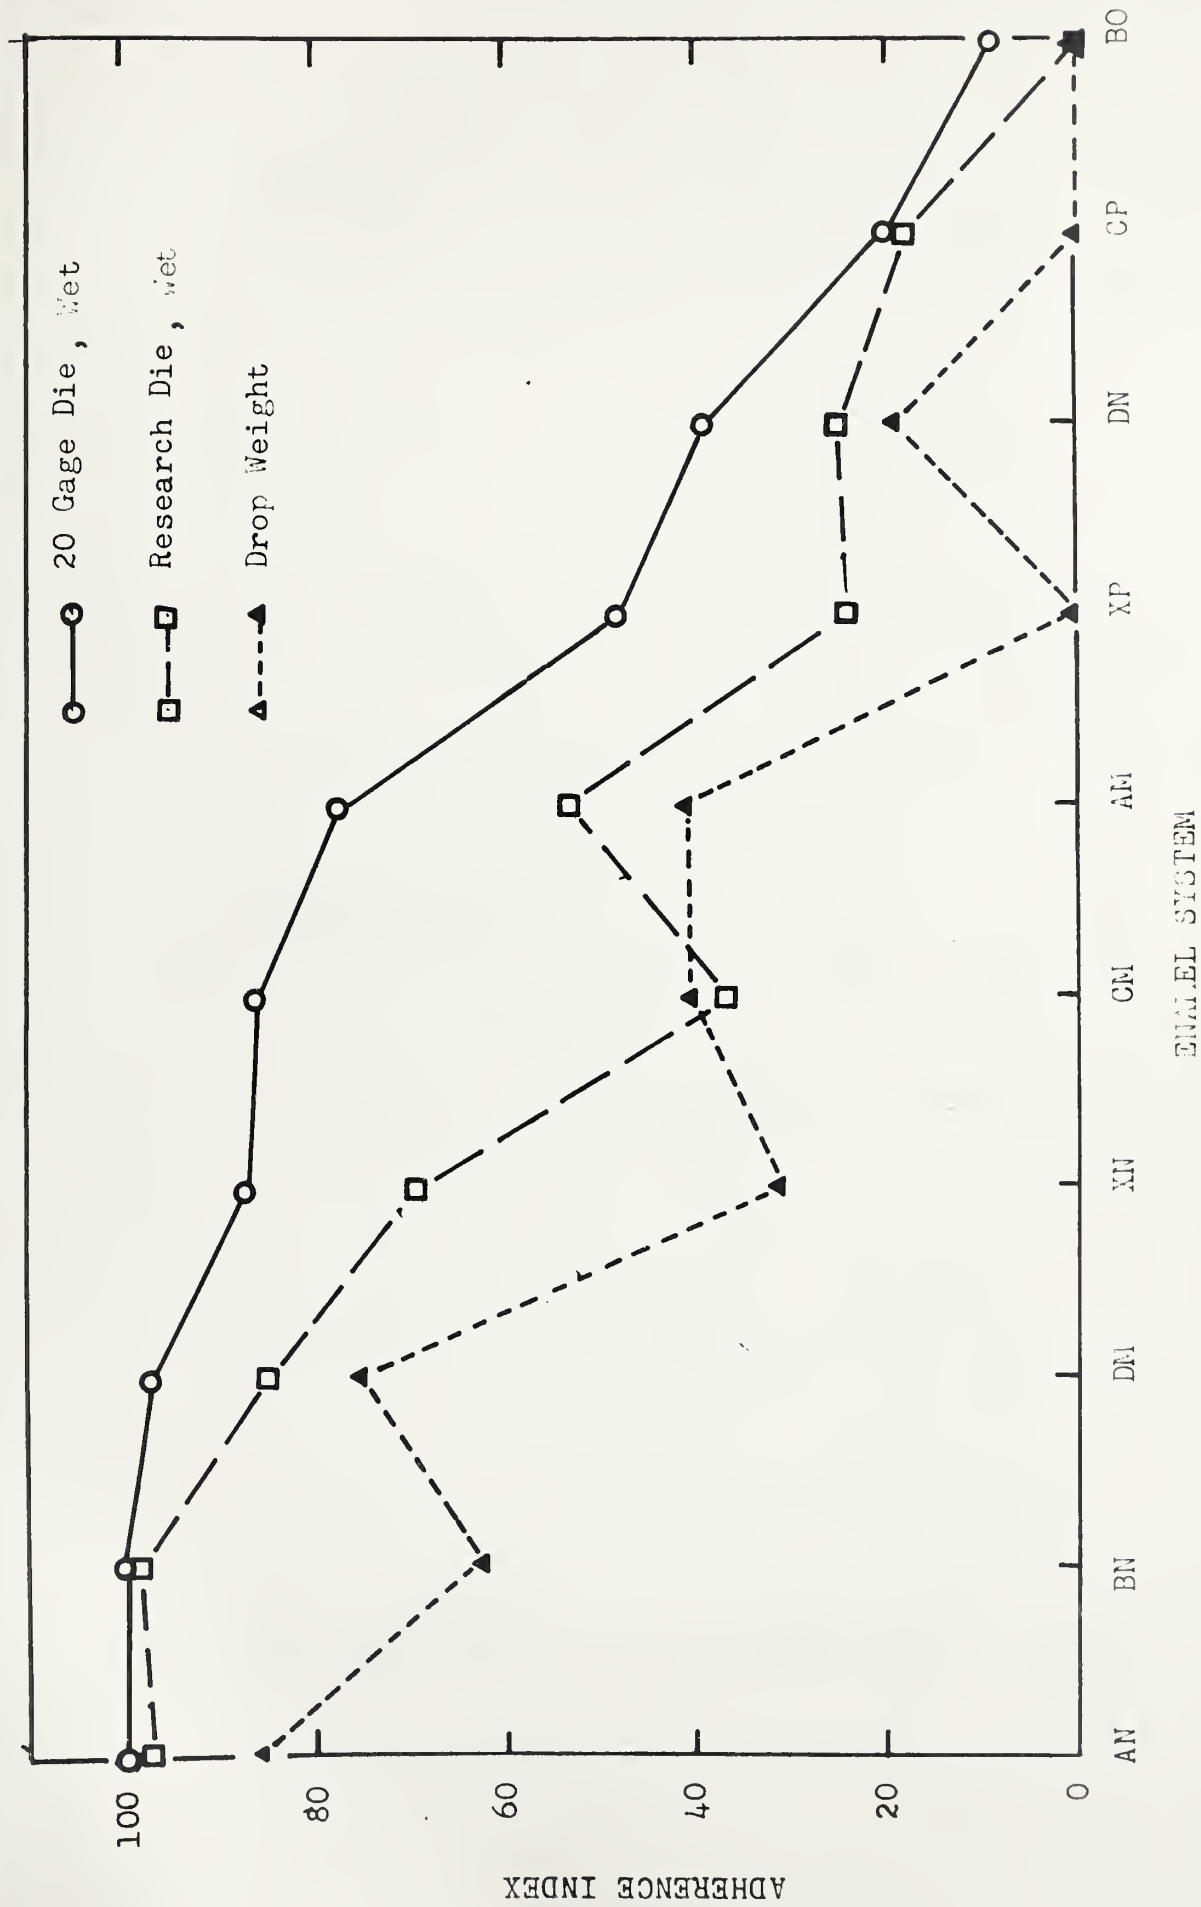


Figure 3. Comparison of Adherence Indices after various Deformation Treatments



#### ENAMEL SYSTEM

Figure 4. Comparison of Adherence Indices after various Deformation Treatments.

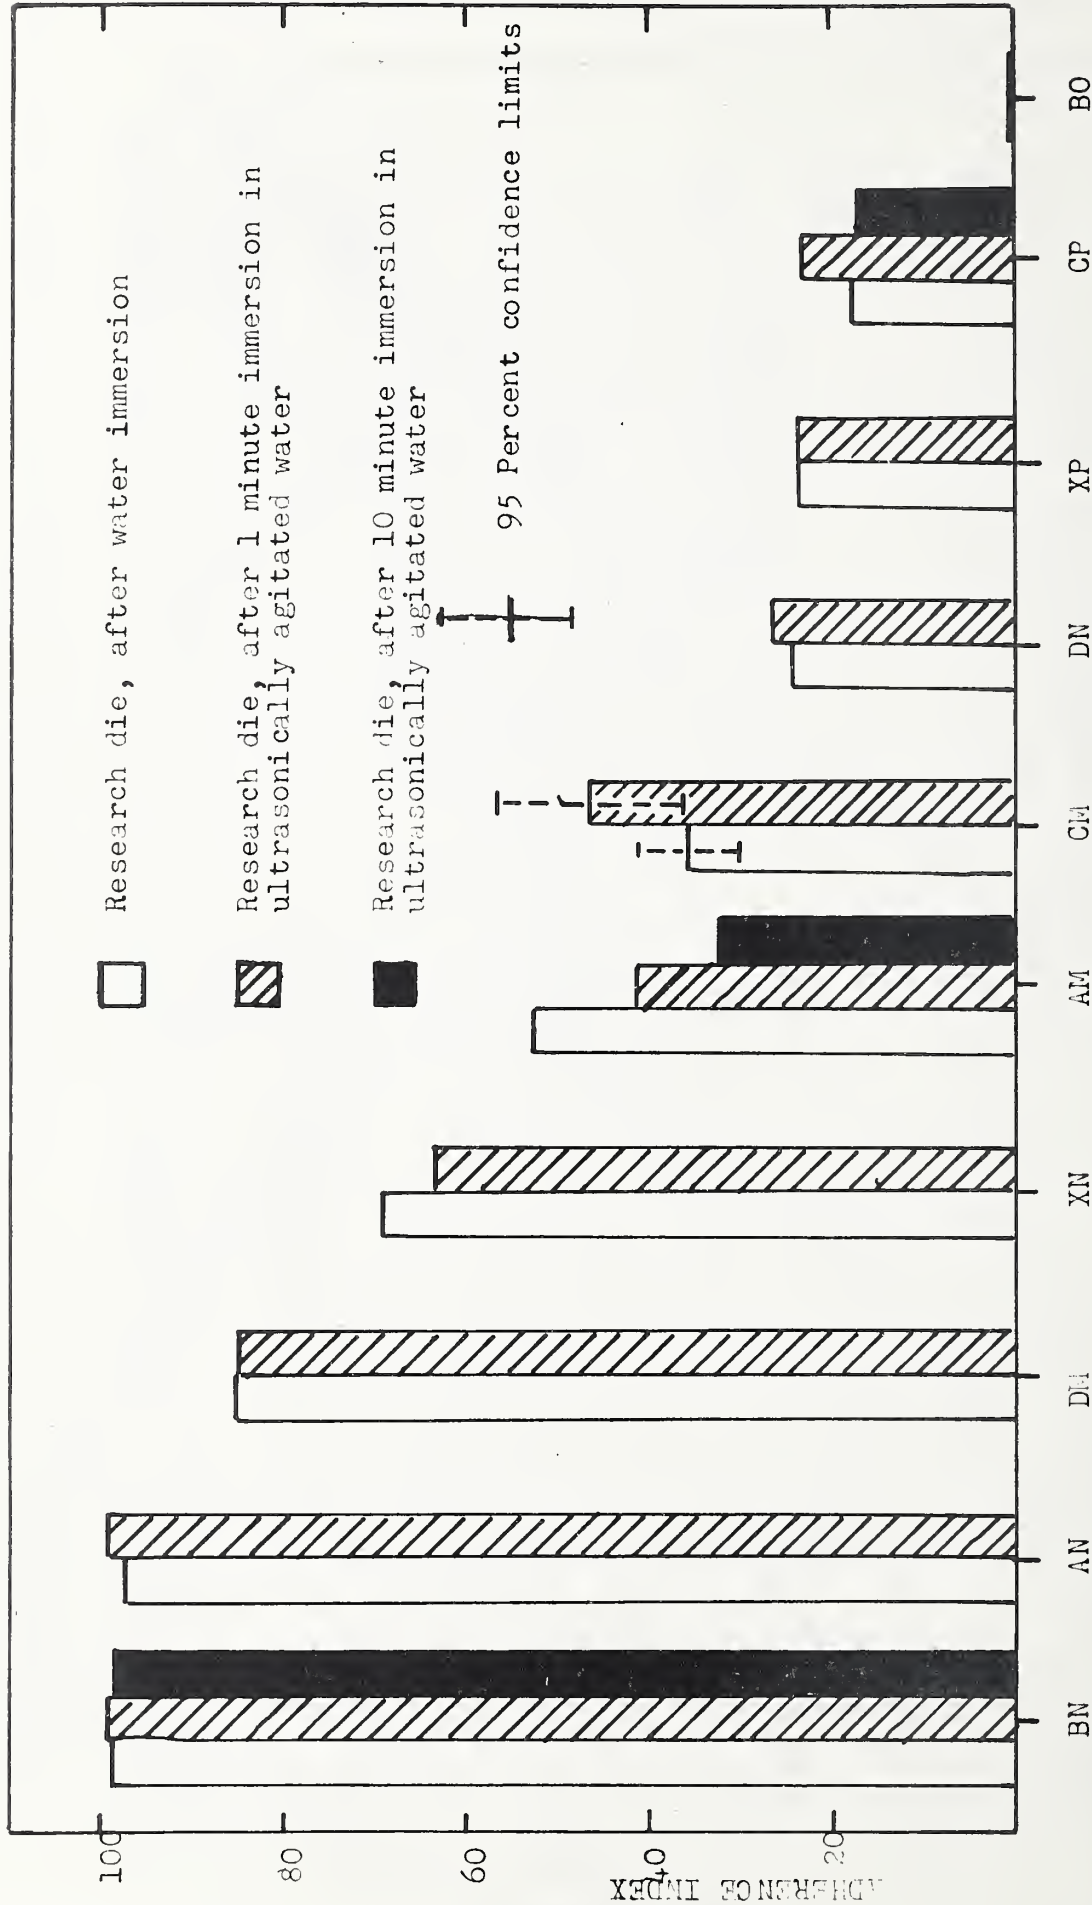



